

Experimental Investigation of Concrete Using Waste Tyre Rubber as Aggregates

Kulwinder Srowa¹, Vikram Dhillon²

¹Student, Dept. of Civil Engg., JCDMCOE, Sirsa, Haryana

²Asst. Prof., Dept. of Civil Engg., JCDMCOE, Sirsa, Haryana

ABSTRACT

Concrete is the most commonly used construction material in the world after water. Concrete is a composite material made of cement paste and aggregates. Aggregates occupy around 70% volume of concrete. The natural aggregates are depleting day by days. To minimise this, natural aggregates should be replaced with the waste materials so that the waste materials can also be utilized and their environmental issue can be minimized. In the present study, rubber aggregates were used in the development of rubberized concrete. The coarse aggregates were replaced with the rubber aggregates by 0%, 10%, 20%, 30% and 40%. The different properties of rubberized concrete of M 25 grade was studied in the present work. The quantity of super plasticizer was 0.50%. Fresh i.e. workability by slump flow test and hardened properties i.e. compressive strength, split tensile strength and flexural strength at 7, 28 and 56 days of curing was studied. Compressive strength, split tensile strength and flexural strength decreased with the increase in rubber aggregates content.

INTRODUCTION

Concrete is the most commonly used construction material in the world after water. Concrete is a composite material made of cement paste and filler materials. Cement paste had portland cement and water and filler materials contains aggregates. Aggregates occupy around 70% volume of concrete. The natural aggregates are depleting day by days. To minimise this, natural aggregates should be replaced with the waste materials so that the waste materials can also be utilized and their environmental issue can be minimized. The remarkable increase in number of vehicles worldwide and lack of both technical and economical mechanism make that waste tire are considered a serious pollution problem in term of waste disposal. Research efforts have been made to match society's needs for economic and safe disposal of waste materials. The use of waste materials saves natural resources and dumping spaces and helps to maintains clean environment.

Discarded vehicle tires constitute the important part of solid waste which were historically disposed into landfills. These waste had an emerging use on the concrete production in which they are being replaced with natural fine or coarse aggregates. This has the additional advantage of saving natural aggregates used in the production of concrete. Recycled waste tire has been used in different application. It has been used as a fuel for cement kiln, in production of carbon black as feedstock and in marine environment as artificial reef. Recycled waste tire rubber is a promising material in the construction industry because it has lightweight, elasticity, energy absorption, sound and heat insulating properties. Rubber can be used in the form of chip or crumb. Rubberized concrete can be used for nailing concrete, as false facades, stone backing, interior construction, in the production of concrete kerb and paving block, in road construction as shock absorber, in sound barrier as sound absorbers as well as in building as an earthquake shock wave absorber, in sidewalks, in flowable fill as bridge abutments fills, trench fills and foundation supports fills. Rubberized concrete can be used where resistance to impact is required such as in railway buffers and pavements. It can also be used in the light weight concrete block.

In the present study, rubber aggregates were used in the development of rubberized concrete. The rubberized concrete consists of cement, fine aggregates, coarse aggregates, water and rubber aggregates. Rubberized concrete had higher crack resistance, sound insulation and thermal resistance but decreased the chloride ion penetration. Rubberized concrete can be used in road construction as shock absorber, in sound barriers as sound absorbers as well as in building as an earthquake shock wave absorber and in sidewalks. Rubber waste is a highly durable material and it is highly resistant to most natural environments.

Lv Jing et.al. (2015) investigated the slump value, compressive strength, flexural strength, static modulus of elasticity and unit weight of rubber light weight aggregates concrete with sand replacement with rubber particles from 10% to

100%. Rubber particles had detrimental effect on the slump and mechanical strength while unit weight dropped. **Agampodi S.M Mendis et.al. (2017)** compared the mechanical behaviours of various crumbed rubber concrete (CRC) mixes of similar strength. Shredded scrap truck tyre was used as crumbed rubber for CRC mixes. Mechanical properties and stress-strain relationships of the developed mixes were experimentally measured and compared. The results showed that CRC mixes exhibited similar mechanical properties regardless of rubber contents. **Nelson Flores Medina et.al. (2016)** studied the influence of high volume of recycled rubber aggregates on acoustic properties of lightweight concrete containing. Concrete specimens were designed with 0–100% substitution of coarse aggregate by two different rubber aggregates from recycled tires. The results showed that combination of steel and textile fibers contaminated with rubber powder increased sound absorption in comparison ordinary or rubberized concrete. **Shah S. F. A. et.al. (2014)** investigated the performance of concrete using rubber waste from scrap tires. Replacement ratio of scrap tire was 5%, 10% and 15% with coarse aggregates. There was no significant changes in concrete properties up to 5% substitution were observed. Beyond 5%, concrete properties change appreciably.

2. EXPERIMENTAL PROGRAMME

Material used

Ordinary portland cement (consistency 30% ,initial setting time 120 min. and final setting time 200 min, fineness 4 and compressive strength of cement at 3, 7 and 28 days was 31.3, 36.56 and 45.23 MPa respectively) was used in the present work.

Natural sand with fineness modulus 2.65, specific gravity 2.58 and zone III was used. Coarse aggregates of size 10mm and 20 mm Of broken stone of specific gravity 2.64 and 2.58 and fineness modulus 6.05 and 6.89 respectively were used. Tap water was used for mixing and curing.

Rubber Aggregates

Rubber aggregates were taken from truck tyres which were manually shredded in the regular size of 15mm. Complast SP430, super plasticizer was used in the present study.

In the present manual mixing was done. The different materials were weighed on the weighting machine. The materials were mixed first when they dry and water was added to the mix and uniformly mixed manually. The mixing time was about 5-6 minutes. The compaction was done by vibratory tables in this work. After mixing and compaction of the concrete mix, the mix was poured into the mould and casted into cubes, cylinders and beams. After 24 hours specimens were withdrawn from the moulds and the specimens were kept in the curing tanks for curing. Casting of moulds for compressive strength test, splitting tensile strength and flexural strength test were done. Three moulds were casted for each mix and cured for 7, 28 and 56 days and then they were tested.

After curing the specimens were taken out from the curing tank and then dried at the room temperature. Then the specimens were tested destructively in the testing machine as per the specification. One controlled mix proportion was prepared without use of recycled aggregates. The coarse aggregates were replaced with 0%, 10%, 20%, 30% and 40% of rubber aggregates. M25 grade of concrete was casted in the present work. The aggregates of size 10 mm and 20 mm and water cement ratio of 0.45 were taken constant for all the mix proportions in the present study. The ratio of 10mm and 20mm aggregates in the concrete mixture was kept 50%-50%. The batch specification is given in the table 3.1.

Table 2.1 Mix proportion of rubberized concrete

Sr. No.	Mix Number	Natural aggregates (%)	Coarse	Rubber Content (%)
1	M1	100		0
2	M2	90		10
3	M3	80		20
4	M4	70		30
5	M5	60		40

3. RESULTS AND DISCUSSION

3.2.1 WORKABILITY

Workability of the rubberized concrete was determined by the slump test. The effect of rubber aggregates on the workability of rubberized concrete is shown in fig 3.1 and table 3.1

Table 3.1 Workability of rubberized concrete

Mix Number	Slump Value(mm)
M1	45
M2	55
M3	65
M4	75
M5	90

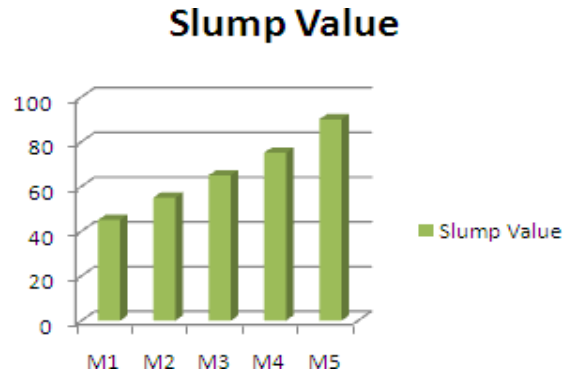


Fig. 3.1 Workability of Rubberized Concrete

3.2.2 COMPRESSIVE STRENGTH

The compressive strength of the different concrete mixes is given in the tabular form in table 3.2 and in fig. 3.2

Table 3.2 Compressive strength of Rubberised concrete

Mix Number	7 days	28 days	56 days
M1	20.45	29.76	36.55
M2	16.32	25.23	31.48
M3	15.21	24.81	30.55
M4	13.98	23.66	29.45
M5	12.78	22.12	28.10

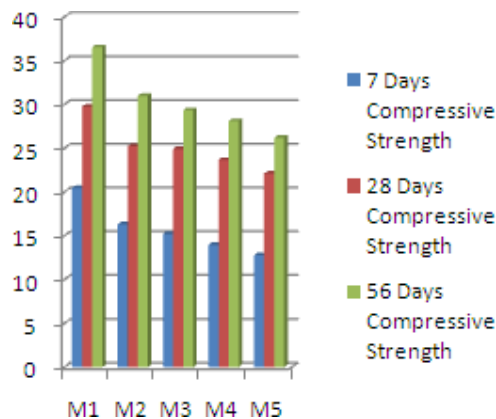


Fig. 3.2 Variation in compressive strength at 7, 28 and 56 days

The compressive strength of rubberized cubes decreased with the increase in rubber aggregates. The compressive strength of rubberized concrete decreased by 20%, 26%, 32% and 38% in comparison to control mix at 7 days due to addition of rubber content in the concrete mixtures. The flexural strength of rubberized concrete decreased by 15%, 17%, 20% and 26% at 28 days and 13%, 16%, 19% and 23% at 56 days with respect to control mix i.e. 0% rubber aggregates in the concrete mixtures.

3.2.3 SPLIT TENSILE STRENGTH

The split tensile strength of different mix proportions are given in table 3.3 and their variation is shown in the fig. 3.3

Table 3.3 Split tensile strength of rubberized concrete

Mix Number	7 days	28 days	56 days
M1	2.3	3.7	4.5
M2	1.86	3.21	3.85
M3	1.75	3.10	3.76
M4	1.63	2.98	3.66
M5	1.55	2.88	3.57

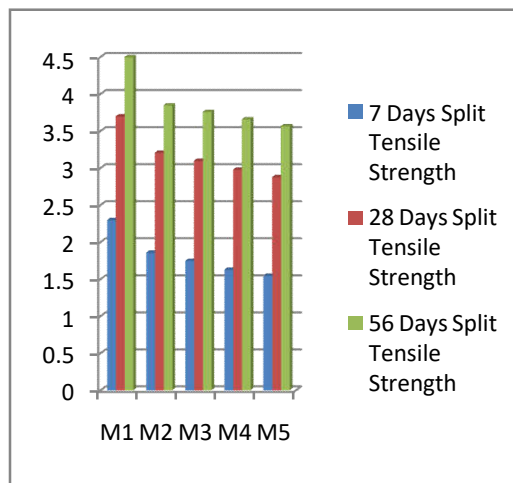


Fig 3.3 Variation in split tensile strength at 7, 28 and 56 days

The split tensile strength of the control mix was highest and it decreased with the increase in rubber aggregates. The split tensile strength of rubber concrete decreased by 19%, 24%, 29% and 33% in comparison to control mix at 7 days due to addition of rubber content in the concrete mixtures. The split tensile strength of rubberized concrete decreased by 13%, 16%, 19% and 22% at 28 days and 14%, 16%, 18% and 21% at 56 days with respect to control mix i.e. 0% rubber aggregates in the concrete mixtures.

3.2.4 FLEXURAL STRENGTH

The flexural strength of the rubber reinforced concrete of beam of different mix proportions are given below in the table 3.4 and the variation of the flexural strength of various mix proportions is shown in fig. 3.4

Table 3.4 Flexural strength of rubberized concrete

Mix Number	7 days(flexural)	28 days	56 days
M1	3.45	4.05	4.50
M2	2.82	3.45	3.91
M3	2.69	3.33	3.8
M4	2.51	3.21	3.69
M5	2.38	3.10	3.57

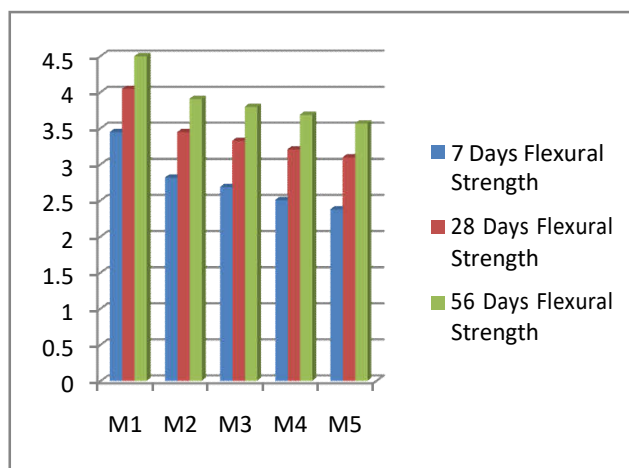


Fig. 3.4 Variation in flexural strength at 7, 28 and 56 days

The flexural strength of rubber concrete decreased by 18%, 22%, 27% and 31% in comparison to control mix at 7 days due to addition of rubber content in the concrete mixtures. The flexural strength of rubberized concrete decreased by 15%, 18%, 21% and 23% at 28 days and 13%, 16%, 18% and 21% at 56 days with respect to control mix i.e. 0% rubber aggregates in the concrete mixtures.

CONCLUSIONS

Rubberized concrete (RC) is a concrete containing cement, aggregates and rubber. In the present study the fresh and hardened properties of rubberized concrete such as compressive strength, split tensile strength and flexural strength at 7, 28 and 56 days with constant water cement ratio of 0.45 and the aggregate was replaced by 0%, 10%, 20%, 30%, 40% rubber aggregates and compared with conventional concrete. The following points were observed from the discussion of the result obtained from this study

- The compressive strength of rubberized concrete decreased by 20%, 26%, 32% and 38% at 7 days, 15%, 17%, 20% and 26% at 28 days and 13%, 16%, 19% and 23% at 56 days respectively for M2, M3, M4 and M5.
- The split tensile strength of rubberized concrete of mix M2, M3, M4 and M5 decreased by 19%, 24%, 29% and 33% at 7 days, 13%, 16%, 19% and 22% at 28 days and 14%, 16%, 18% and 21% at 56 days as compared to mix M1.
- The flexural strength of rubberized concrete decreased in comparison to control mix by 18%, 22%, 27% and 31% at 7 days, 15%, 18%, 21% and 23% at 28 days and 13%, 16%, 18% and 21% at 56 days when 10%, 20%, 30% and 40% rubber aggregates were used in place of coarse aggregates.

REFERENCES

- [1]. Aziz Farah Nora Aznieta Abd., Bida Sani Mohammed, Nasir Noor Azline Mohd., Jaafar Mohd Saleh, "Mechanical properties of lightweight mortar modified with oil palm fruit fibre and tire crumb", *Construction and Building Materials*, vol. 73, 2014, pp. 544–550
- [2]. Aiello M.A., Leuzzi F., "Waste tyre rubberized concrete: Properties at fresh and hardened state", *Waste Management*, vol 30, 2010, pp. 1696–1704
- [3]. Azevedo F., Torgal F. Pacheco, Jesus C., Aguiar J.L. Barroso de, Camoes A.F., "Properties and durability of HPC with tyre rubber wastes", *Construction and Building Materials*, vol. 34, 2012, pp. 186–191
- [4]. Bignozzi M.C., Sandrolini F., "Tyre rubber waste recycling in self-compacting concrete, ", *Cement and Concrete Research*, vol. 36, 2006, pp. 735–739
- [5]. Boudaoud Zeineddine, Beddar Miloud, "Effects of Recycled Tires Rubber Aggregates on the Characteristics of Cement Concrete", *Open Journal of Civil Engineering*, 2012, vol2, pp 193-197
- [6]. Centonze G., Leone M., Aiello M.A., "Steel fibre from waste tires as reinforcement in concrete: A mechanical characterization", *Construction and Building Materials*, vol. 36, 2012, pp. 46–57
- [7]. Caggiano Antonio, Xargay Hernan, Folino Paula, Martinelli Enzo, "Experimental and numerical characterization of the bond behaviour of steel fibre recovered from waste tires embedded in cementitious matrices", *Cement & Concrete Composites*, vol 62, 2015, pp. 146–155
- [8]. Flores Medina Nelson, Flores-Medina Darío, Hernandez-Olivares F., "Influence of fibers partially coated with rubber from tire recycling as aggregate on the acoustical properties of rubberized concrete", *Construction and Building Materials*, vol. 129, 2016, pp. 25–36
- [9]. Gesoglu Mehmet, Güneysisi Erhan, Hansu Osman, SüleymanIpek, Asaad Diler Sabah, "Influence of waste rubber utilization on the fracture and steel–concrete bond strength properties of concrete", *Construction and Building Materials*, vol. 101, 2015, pp. 1113–1121

- [10]. Gesoglu Mehmet, Guneyisi Erhan, Khoshnaw Ganjeena, Suleyman Ipek, “Investigating properties of pervious concretes containing waste tire rubbers”, *Construction and Building Materials*, vol. 63, 2014, pp. 206–213
- [11]. Garcia D., Lopez J., Balart R., Ruseckaite R.A., Stefani P.M., “Composites based on sintering ricehusk–waste tire rubber mixtures”, *Materials and Design*, vol. 28, 2007, pp. 2234–2238
- [12]. Ghernouti Youcef, Rabehi Bahia, Bouziani Tayeb, Ghezraoui Hicham, Makhloufi Abdelhadi, “Fresh and hardened properties of self-compacting concrete containing plastic bag waste fibers (WFSCC)”, *Construction and Building Materials*, vol. 82, 2015, pp. 89–100
- [13]. Gupta Trilok, Chaudhary Sandeep, Sharma Ravi K., “Assessment of mechanical and durability properties of concrete containing waste rubber tire as fine aggregate”, *Construction and Building Materials*, volume 73, 2014, pp. 562–574
- [14]. Gupta Trilok, Sharma Ravi K., Chaudhary Sandeep, “Impact resistance of concrete containing waste rubber fiber and silica fume”, *International Journal of Impact Engineering*, vol. 83, 2015, pp. 76-87
- [15]. IS 8112-1989, Specification for 43 Grade Ordinary Portland Cement, Bureau of Indian Standard, New Delhi.
- [16]. IS: 383-1963, “Indian Standard Specification for Coarse and Fine Aggregates from Natural Sources for Concrete, Bureau of Indian Standard, New Delhi.
- [17]. IS: 456-2000, “Indian Standard Code of practice for plain and reinforced concrete, (Second Revision), Bureau of Indian Standard, New Delhi.
- [18]. IS: 5816-1999, “Method of Test for splitting tensile strength of concrete cylinders” Bureau of Indian Standard, New Delhi. 53
- [19]. Kelestemur Oguzhan, “Utilization of waste vehicle tires in concrete and its effect on the corrosion behaviour of reinforcing steels”, *International Journal of Minerals, Metallurgy and Materials*, Volume 17, Number 3, June 2010, Page 363
- [20]. Kalkan Ekrem, “Preparation of scrap tire rubber fiber–silica fume mixtures for modification of clayey soils”, *Applied Clay Science*, 80–81, 2013, pp. 117–125
- [21]. Kotresh K.M, Belachew Mesfin Getahun, “Study On Waste Tyre Rubber As Concrete Aggregates”, *International Journal of Scientific Engineering and Technology* Volume No.3 Issue No.4, 2014, pp 433-436
- [22]. Lv Jing, Zhou Tianhua, Du Qiang, Wu Hanheng, “Effects of rubber particles on mechanical properties of lightweight aggregate concrete”, *Construction and Building Materials*, vol. 91, 2015, pp. 145–149
- [23]. Lijuan Li, Shenghua Ruan, Lan Zeng,” Mechanical properties and constitutive equations of concrete containing a low volume of tire rubber particles”, *Construction and Building Materials*, vol. 70, 2014, pp. 291–308
- [24]. Lia Guoqiang, Garrick Gregory, Eggers John, Abadie Christopher, Stubblefield Michael A., Pang Su-Seng, “Waste tire fiber modified concrete”, vol. 35, 2004, pp. 305–312
- [25]. Lanzón Marcos, Cnudde Veerle, Kock Tim De, Dewanckeke Jan, “Microstructural examination and potential application of rendering mortars made of tire rubber and expanded polystyrene wastes”, *Construction and Building Materials*, vol. 94, 2015, pp. 817–825
- [26]. Mendis Agampodi S.M, Al-Deen Safat, Ashraf Mahmud, “Behaviour of similar strength crumbed rubber concrete (CRC) mixes with different mix proportions”, *Construction and Building Materials*, vol. 137, 2017, pp. 354–366
- [27]. Moustafa Ayman, Elgawady Mohamed A., “Mechanical properties of high strength concrete with scrap tire rubber”, *Construction and Building Materials*, vol. 93, 2015, pp. 249–256